

The structural and electronic properties of germanium clathrates

Jijun Zhao, Alper Buldum, Jianping Lu

Department of Physics and Astronomy, University of North Carolina at Chapel Hill

C.Y.Fong

Department of Physics, University of California at Davis

(February 1, 2008)

The structural and electronic properties of germanium clathrates Ge_{46} and K_8Ge_{46} are studied by first principles calculations within the local density approximation. The equilibrium structures are obtained by *ab initio* pseudopotential calculation combined with dynamic minimizations. The clathrate structure is found as a low energy phase for germanium. The electronic band structures for Ge_{46} clathrates are calculated and the band gap is found to be considerably larger than that of the diamond phase. Due to the effect of pentagonal rings, strong similarity in electronic properties between clathrate and Ge_{24} fullerene structure are found. The effect of doping clathrate cages with metal atoms are examined. The K_8Ge_{46} clathrate is found to be metallic with the conduction bands only slightly modified by K dopants.

71.20.Tx, 61.48.+c

I. INTRODUCTION

The Si and Ge clathrates can be viewed as covalent fullerene solids which is composed of three-dimensional networks of fullerene cages connected by face sharing. The silicon clathrate compounds M_xSi_{46} and $\text{M}_x\text{Si}_{136}$ ($\text{M}=\text{Na}, \text{K}, \text{Rb}, \text{and Cs}$) were first synthesized in 1965¹. The structures of semiconductor clathrates can be classified into two cubic structural types with 46 atoms or 136 atoms per unit cell¹. As shown in Fig.1, the type I clathrate (Clathrate-46) is formed by two smaller 14-face pentagonal dodecahedra (12 five-fold rings, I_h) and six larger 16-face tetrakaidecahedra (12 five-fold rings and 2 six-fold rings, D_{6d}). The structure of type II clathrate (Clathrate-136) consists of sixteen smaller pentagonal dodecahedra (12 five-fold rings, I_h) and eight larger hexakaidecahedra (12 five-fold rings and 4 six-fold rings, T_d). Electronic structure calculations based on different methods have shown that these two open network structures have similar electronic properties^{2,3}.

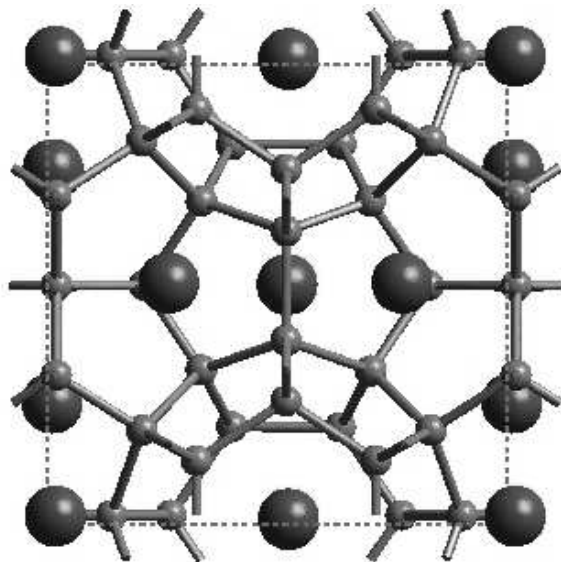


FIG. 1. Atomic structure of fully-relaxed K_8Ge_{46} clathrate. Lattice constant of the simple cubic cell is 10.45 Å.

The research interests of semiconductor clathrates come from several aspects: (1) possible alteration of electronic structures and energy gap from standard diamond form^{2,3}, (2) metal-insulator transition in $\text{M}_x\text{Si}_{136}$ with different concentration of metallic impurity^{4,5}, (3) the finding of superconductivity behavior in $\text{Na}_x\text{Ba}_y\text{Si}_{46}$ ⁶, (4) candidate for thermoelectric applications⁷, (5) template to form three dimensional arrays of nanosized clusters⁸, (6) similarity in structural and electronic properties between semiconductor clathrates and nanoclusters^{9,10}.

There are lots of the experimental and theoretical studies on Si_{46} and Si_{136} clathrates and their compounds¹⁻²¹. The structural, electronic and vibrational properties of Si clathrates are investigated at various theoretical levels ranging from *ab initio*^{2,9,11,12} to tight-binding^{3,13} and empirical potential¹⁴. The most interesting result from those calculations is that the band gap is about 0.7 eV higher than that of diamond phase. Experimental works on Si clathrates include resistivity and magnetization⁶, transport properties⁷, photoemission spectroscopy¹⁰, NMR¹⁵⁻¹⁷, Raman^{18,19}, ESR²⁰, neutron scattering²¹ etc.

In contrast to the intensive studies on silicon clathrates, our current knowledge on germanium clathrates is rather limited. Recently, the germa-

niun clathrate compounds such as K_8Ge_{46} , $\text{Rb}_x\text{Ge}_{46}$, $\text{Na}_x\text{Ge}_{136}$, $\text{Cs}_8\text{Na}_{16}$ have been synthesized and their structures are analyzed with X-ray diffraction^{22,23}. An empirical potential calculation has been performed on pure germanium clathrates¹⁴. However, there is no first principles electronic structure calculation and their fundamental electronic properties are still unclear theoretically. In this work, we report results of first principles study on the structures and electronic properties of Ge_{46} and K_8Ge_{46} clathrates. The equilibrium structure, electronic band and band gap, electronic density of states and electron density distribution are obtained and discussed.

II. COMPUTATIONAL METHODS

First principles SCF pseudopotential method^{24–26} is used to perform static calculation on the electronic structures and total energy of Ge_{46} and K_8Ge_{46} in ideal clathrate structures with different lattice constants. The ion-electron interaction is modeled by numerical BHS norm-conserving nonlocal pseudopotential²⁷ in the Kleinman-Bylander form²⁸. The Ceperley-Alder’s exchange-correlation parameterized by Perdew and Zunger is used for the LDA in our program²⁹. The kinetic energy cutoff for plane-wave basis is chosen as 12 Ryd. Ten symmetric $\mathbf{k}$ points generated in Monkhorst-Pack spirit³⁰ are employed to sample the Brillouin zone.

From the static calculation, the equation of states with ideal crystal structures and the equilibrium lattice constants are obtained. These ideal structures are further optimized by using structural minimization via conjugate gradient technique (CASTEP³¹). The CASTEP program is based on plane-wave pseudopotential technique. It can relax the atomic position by computing the force acting on atoms from electronic calculation and moving atoms efficiently in a numerical way²⁵.

III. THE STRUCTURES AND BAND GAPS OF Ge_{46}

In Fig.2, we present the equation of states for both Ge_{46} clathrate and diamond phase that is obtained from first principles static calculations. We find that the Ge_{46} clathrate is a locally stable structure and its energy is only about 0.08 eV per atom higher than that of diamond phase. For comparison, the β -tin phase of germanium is about 0.25 eV higher in energy than the diamond phase²⁴. The low energy feature of clathrate phase is a natural consequence of its four coordinate characteristics and may be partially attributed to the softness of the bond-bending distortion modes⁹. As compared to diamond structure, the volume per atom in the clathrate phase is increased by about 14.8%. All of these results are very close to the previous empirical potential simulation on Ge_{46} , in which the change of atomic volume in

type I clathrate is 15.3 % and its energy is 0.071 eV per atom higher than diamond¹⁴.

Table I The structural properties and band gaps of perfect and relaxed clathrate compared with previous LDA local orbital (LDA-LO) and tight-binding molecular dynamics (TBMD) calculation on Si_{46} clathrate. V/V_0 is the reduced atomic volume. l denotes the Ge–Ge bond length. a is the equilibrium lattice constant. E_g is the electronic band gap (indirect gap for both diamond and clathrates). The numbers in brackets are experimental values^{33,22}.

	V/V_0	l (Å)	a (Å)	E_g (eV)
Ge Diamond	1.00	2.407	5.56 (5.66)	0.40
Ge_{46} (ideal)	1.148	2.375, 2.540	10.43	1.25
Ge_{46} (relaxed)	1.128	2.380 $\sim$ 2.433	10.37	1.46
K_8Ge_{46} (ideal)	1.271	2.562, 2.739	10.79	–
K_8Ge_{46} (relaxed)	1.155	2.346 $\sim$ 2.492	10.45 (10.66)	–
Si_{46} (LDA-LO) ²	1.17	2.38 $\sim$ 2.43	10.35	2.50
Si_{46} (TBMD) ³	1.14	2.367	10.20	1.82

In previous theoretical study on bulk silicon and germanium of various phases²⁴, considerable similarity in the bonding behavior and phase diagram are found between silicon and germanium. In Table I, we summarize our results on the structural properties and band gaps for perfect and relaxed Ge_{46} and K_8Ge_{46} clathrate and compare them with the previous LDA and tight-binding calculations on Si_{46} clathrate^{2,3,9}. We find the difference of volume and energy between clathrate and diamond phase for germanium and silicon are comparable.



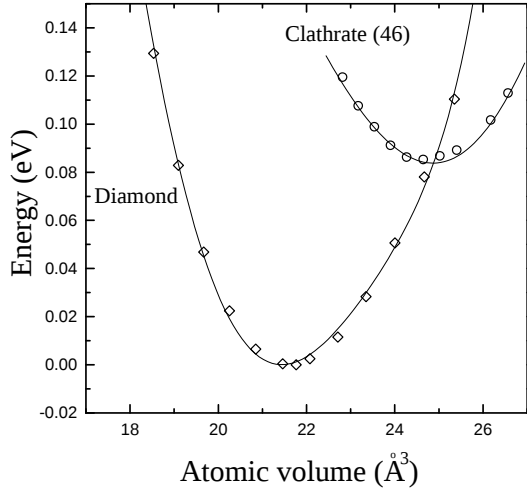


FIG. 2. Energy per atom of diamond and Ge_{46} clathrate as a function of atomic volume.

The ideal clathrate structure for the Ge_{46} at equilibrium lattice constant is further optimized with CASTEP plane-wave pseudopotential calculation. Both atomic positions and unit cell parameters are allowed to relax. The SCF pseudopotential code used in static calculation has also been used to test the total energy for the initial and final structure and the results agree with CASTEP calculations. After optimization, the lattice constant of simple cubic unit cell decreases from $10.43 \text{ \AA}$ to $10.37 \text{ \AA}$. The relative atomic positions are only slightly relaxed from their initial configuration. The range of bond length distribution has also been narrowed, i.e., from the $2.375 \text{ \AA} \sim 2.540 \text{ \AA}$ in ideal clathrate structure to $2.38 \text{ \AA} \sim 2.433 \text{ \AA}$.

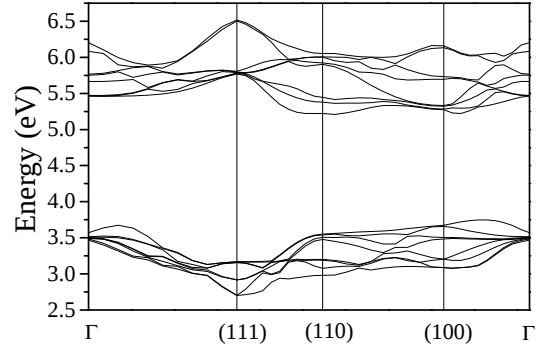

(a)

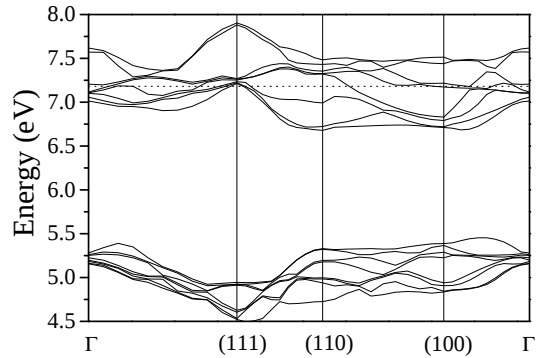

(b)

FIG. 3. Electronic band structure for (a) Ge_{46} , (b) K_8Ge_{46} clathrate near Fermi level.

The electronic band structure calculations are carried

out for Ge_{46} clathrate with the equilibrium structure. The near band-gap band structures for the minimum energy configurations of Ge_{46} clathrates are plotted in Fig.3(a). Both the valence band maximum and conduction band minimum are located on the Γ to X line and they are very close in $\mathbf{k}$ space. An indirect gap of 1.46 eV is found. As for bulk germanium in diamond phase, our calculations have yielded an indirect band gap of 0.40 eV between L and Γ points. The underestimation of band gap is a common feature of LDA calculations. Nevertheless, our current results suggests that the band gap of Ge_{46} phase is about 1 eV higher than that of the diamond phase, which is similar to the 0.7 eV increment in band gap found for Si_{46} and Si_{34} clathrates^{2,3,9,10}. Furthermore, the electronic band structure of Ge_{46} clathrate are calculated independently via a simple tight-binding model. The tight-binding hopping parameters for germanium are taken from Ref.[32] and the parameters for nearest neighboring atoms in clathrate structure is assumed to be the same as that in diamond. According to tight-binding calculation, the band gap of diamond is 1.13 eV and the gap for relaxed clathrate Ge_{46} is 2.93 eV. Although the tight-binding method usually overestimate the band gap of a system, the increment of 1.80 eV in the band gap from tight-binding model is in reasonable agreement with *ab initio* calculation. Therefore, we expect that the true increase of band gap Δ from diamond to Ge_{46} clathrate phase might be between the LDA and TB prediction, i.e., $1.06 \text{ eV} \leq \Delta \leq 1.80 \text{ eV}$. This result suggests that the clathrate materials might be useful in the new electronic and optical application in the future.

Since the Ge_{46} clathrate structure is essentially a 3D network composed by Ge_{20} and Ge_{24} cages with face sharing, it is interesting to compare the electronic properties of the individual Ge_{20} and Ge_{24} cages with that of the clathrate. SCF pseudopotential electronic structure calculations on isolated Ge_{20} and Ge_{24} clusters in fullerene cages are performed. The clusters are placed in a large simple cubic supercell with length of 28 a.u. In Fig.4, we present the calculated electronic density of states (DOS) for Ge_{20} and Ge_{24} cages along with DOS for diamond and Ge_{46} . The detailed analysis are given in the following.

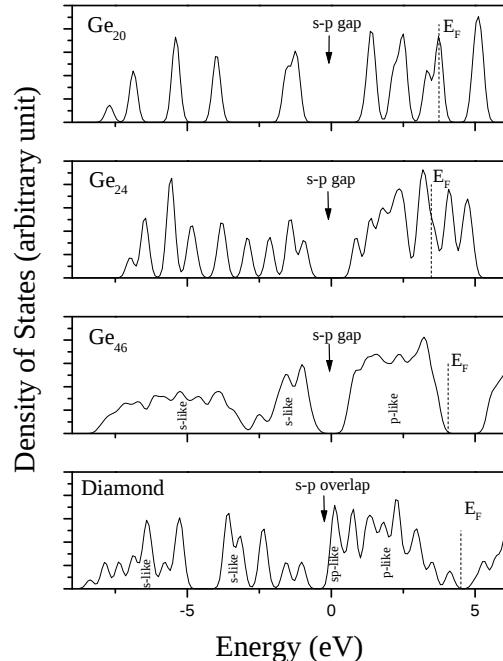


FIG. 4. Electronic density of states (DOS) of Ge_{20} , Ge_{24} fullerene, bulk germanium in Ge_{46} clathrate and diamond phases Gaussian broadening of 0.136 eV is used.

Firstly, we find that most of the peaks in the DOS of Ge_{46} can be assigned to Ge_{24} , while the DOS of Ge_{20} also show some similarity with Ge_{46} . The DOS of Ge_{24} is closer to that of clathrate because most atoms in clathrate are associated with Ge_{24} cage. The presence of s-p gap in due to the large number of five-member rings in the cage and clathrate structure. This remarkable similarity implies that the Ge_{46} clathrate can be taken as the small Ge fullerene assembled solid with both geometrical and electronic hierarchy. However, both the Ge_{24} and Ge_{20} cages are not semiconductor systems and do not have open band gaps like Ge_{46} clathrates. The band splitting in Ge_{46} can be attributed to the sharing of face atoms by Ge_{20} and Ge_{24} and the interaction between neighboring fullerene cages.

On the other hand, we can compare the DOS of clathrate and diamond in Fig.4. Several significant differences can be found. Besides the improvement of band gap in clathrate upon diamond phase, the total width of valence band of Ge_{46} (about 12 eV) is narrower than that of diamond (about 13 eV). This phenomenon has been also predicted in Si_{46} clathrate⁹ and observed experimentally¹⁰. We also found a gap opening between the s-like and p-like states in the case of Ge_{46} clathrates as well as Ge_{20} , Ge_{24} clusters, while *s* and *p* states are overlapped in the DOS of diamond. These remarkable differences in the electronic structure of clathrate and diamond can be understood by the large portion of five-

fold ring in clathrate structure. In the diamond lattice consisting of 100% six-fold ring, the $4s$ orbital can form complete antibonding states, which can distribute to high energy and overlap with the lower $4p$ -like states. In contrast to diamond, the Ge_{46} clathrate is composed of 87% five-fold rings and 13% six-fold rings. In the five-fold ring, $4s$ orbital cannot form complete antibonding states so that the top of $4s$ -like states is still lower in energy than the bottom of $4p$ -like and a gap between s and p states inside valence band opens. The similar effect of five-fold ring on the $4p$ bonding orbitals will induce the incompleteness of $4p$ -like states. As a consequence, the valence band top of Ge_{46} is lower than that of diamond, which corresponds to the narrowing of valence band width and broadening of fundamental gap between valence and conduction band. The novel electronic properties caused by five-fold ring and the similarity between clathrate and fullerene cages may be explored for future electronic and optical applications.

IV. ELECTRONIC STRUCTURES OF K_8Ge_{46} CLATHRATE

Although the pure silicon and germanium semiconductor clathrates are predicted to be locally stable, experiments have only synthesized the metal-doped clathrate compounds of Si and Ge. The metallic impurity atoms inside the clathrate might influence the electronic properties of clathrate due to the interaction between the metal atoms and semiconductor skeleton. Here we have chosen the K_8Ge_{46} clathrate as such a model system to study the doping effect on germanium clathrate.

The structural properties of K_8Ge_{46} are studied with the same procedure we have applied on Ge_{46} clathrate: a static calculation of equation of states followed by a full relaxation. The minimized structure of K_8Ge_{46} clathrate is shown in Fig.1 and the structural parameters of this minimum energy configuration is given in Table I. It is natural to find that the lattice constant of cubic unit cell for K_8Ge_{46} clathrate is larger than pure Ge_{46} clathrate in both ideal and relaxed structure because of the K atoms inside the fullerene cage. We also find a decrease of lattice constant from $10.79 \text{ \AA}$ to $10.45 \text{ \AA}$ after structure minimization. The minimized lattice constant ($10.45 \text{ \AA}$) for the K_8Ge_{46} is in good agreement with experimental value ($10.66 \text{ \AA}$)²². During the minimization, the geometries of K_8Ge_{46} relax from the perfect clathrate network a little more than that happened in the Ge_{46} .

First principles SCF pseudopotential electronic structure calculation has been performed on the relaxed K_8Ge_{46} clathrate. In Fig.3(b), we presented the electronic band structure of K_8Ge_{46} near Fermi level. The system is found as metallic due to the K dopants. We can further examine the highest valence bands and lowest conduction bands of Ge_{46} and K_8Ge_{46} shown in Fig.3(a) and (b) in detail. The valence bands of K_8Ge_{46} are very

closed to the original bands in Ge_{46} , while the conduction band structures have been slightly modified upon the inclusion of K atoms.

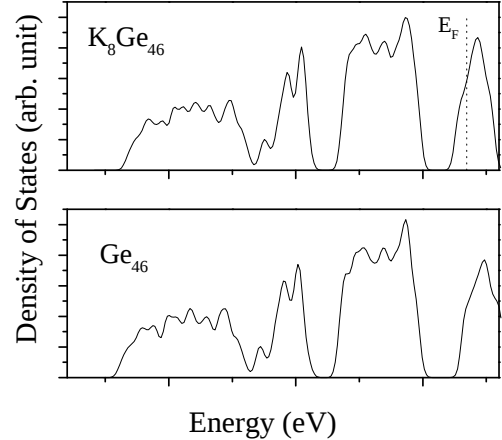


FIG. 5. Electronic density of states (DOS) of Ge_{46} and K_8Ge_{46} clathrate. Gaussian broadening of 0.136 eV is used. Note the similarity in the two DOS.

We also study the difference of the electronic properties between the pure and doped systems by comparing their the electronic density of states (DOS). The density of states for Ge_{46} and K_8Ge_{46} clathrate are compared in Fig.5. The DOS of valence electrons in K_8Ge_{46} is very close to that in Ge_{46} while the DOS for conduction electrons of K_8Ge_{46} are somewhat different from that in Ge_{46} . On the other hand, the gap between valence and conduction band is 0.23 eV narrower in the case of K_8Ge_{46} .

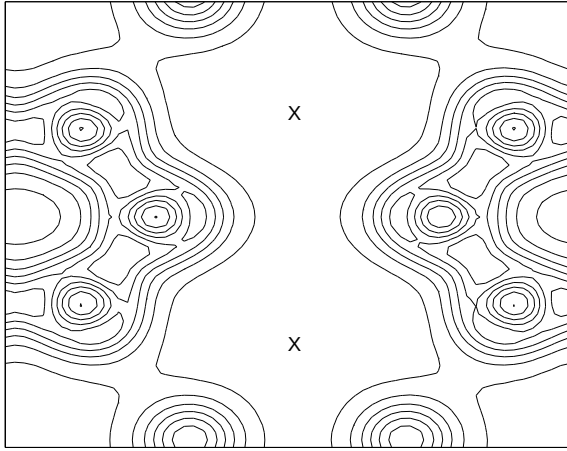


FIG. 6. Contour plots of the electron densities of K_8Ge_{46} on the (100) plane. No charge density is found at K site (marked by X), indicating complete charge transfer.

The analysis on the charge transfer and chemical bonding effects have been presented in the contour plots of the electron densities of K_8Ge_{46} on the (100) plane in Fig.6. We have also calculated the charge density distribution of Ge_{46} and find it is very close to that of K_8Ge_{46} . As shown in Fig.6, there is almost no charge sitting on K sites. This result is consistent with previous calculation on $Na_2Ba_6Ge_{46}$ ⁹, which found a rather simple charge transfer from Na to the Si skeleton. In their calculation, some hybridization are found between Ba and Si since Ba atoms has some low lying $5d$ orbitals⁹. This difference also corresponds to the DOS and other electronic properties. A high DOS peak at Fermi energy is found for $Na_2Ba_6Ge_{46}$ ⁹ and this material is superconducting⁶. In comparison, the DOS at Fermi level for K_8Ge_{46} is moderate and it is not superconducting.

V. CONCLUSIONS

We have used first principles SCF pseudopotential method to investigate the structural and electronic properties of Ge_{46} and K_8Ge_{46} clathrates. The main conclusion of this work can be made as follows:

(1) Germanium clathrate Ge_{46} is found to be a locally stable structure with its energy only slight higher than that of diamond phase, and its atomic volume is about 13% larger than diamond phase.

(2) Ge_{46} clathrate shows an indirect band gap along Γ -X direction that is about 1 eV higher than the band gap of diamond phase. The pentagonal rings in the clathrate structure cause the valence band structure of Ge_{46} clathrate to be similar to that of Ge_{24} fullerene cage. The open covalent network structures contribute to the large band gaps.

(3) The K_8Ge_{46} clathrate is metallic with a moderate density of states. The valence band structures and DOS are similar to those of the pure Ge_{46} , while the conduction bands are modified due to the K dopants. Almost

complete charge transfer from K sites to Ge frames is found in the K_8Ge_{46} clathrate.

ACKNOWLEDGMENTS

This work is supported by the U.S. Army Research Office (Grant DAAG55-98-1-0298) and Department of Energy (Grand DEFG02-96ER45560). The authors thank O.Zhou for helpful discussions. We acknowledge computational support from the North Carolina Supercomputer Center.

- ¹ J.S.Kasper, P.Hagenmuller, M.Pouchard, and C. Cros, *Science***150**, 1713(1965).
- ² G.B.Adams, M.O'Keeffe, A.A.Demkov, O.F.Sankey and Y.Huang, *Phys.Rev.***B49**, 8048(1994).
- ³ M.Menon, E.Richter, K.R.Subbaswamy, *Phys.Rev.***B56**, 12290(1997).
- ⁴ N.F.Mott, *J.Solid State Chem.***6**, 348(1973).
- ⁵ S.B.Roy, K.E.Sim, and A.D.Caplin, *Philos.Mag.***B65**, 1445(1992).
- ⁶ H. Kawaji, H.Horie, S.Yamanaka, and M.Ishikawa, *Phys.Rev.Lett.***74**, 1427(1995).
- ⁷ G.S.Nolas, J.L.Cohn, G.A.Slack and S.B.Schujman, *Appl.Phys.Lett.***73**, 178(1998).
- ⁸ A.A.Demkov and O.F.Sankey, *Chem.Mater.***8**, 1793(1996).
- ⁹ S.Saito and A.Oshiyama, *Phys.Rev.***B51**, 2628(1995); S.Saito, *Mater.Sci.Forum***232**, 233(1996).
- ¹⁰ P.Melinon, P.Keghelian, X.Blase, J.Le Brusca, A.Perez, E.Reny, C.Cros, and M.Pouchard, *Phys.Rev.***B58**, 12590(1998).
- ¹¹ A.A.Demkov, O.F.Sankey, K.E.Schmidt, G.B.Adams, and M.O'Keeffe, *Phys.Rev.***B50**, 17001(1994).
- ¹² V.I.Smelyansky and J.S.Tse, *Chem.Phys.Lett.***264**, 459(1997).
- ¹³ D.Kahn and J.P.Lu, *Phys.Rev.***B56**, 13898(1997).
- ¹⁴ M.O'Keeffe, G.B.Adams, O.F.Sankey, *Phil.Mag.Lett.***78**, 21(1998).
- ¹⁵ F.Shimizu, Y.Maniwa, K.Kume, H.Kawaji, S.Yamanaka and M.Ishikawa, *Phys.Rev.***B54**, 13242(1996).
- ¹⁶ J.Gryko, F.McMillan and O.F.Sankey, *Phys.Rev.***B54**, 3037(1996).
- ¹⁷ J.Gryko, P.F.McMillan, R.F.Marzke, A.P.Dodokin, A.A.Demkov and O.F.Sankey, *Phys.Rev.***B57**, 4172(1998).
- ¹⁸ S.L.Fang, L.Grigorian, P.C.Eklund, G.Dresselhaus, M.S.Dressehaus, H.Kawaji, and S.Yamanaka, *Phys.Rev.***B57**, 7686(1998).
- ¹⁹ Y.Guyot, B.Champagnon, E.Reny, C.Cros, M.Pouchard, P.Melinon, A.Perez, I.Gregora, *Phys.Rev.***B57**, 9475(1998).
- ²⁰ H.Yahiro, K.Yamaji, M.Shiotani, S.Yamanaka, M.Ishikawa, *Chem.Phys.Lett.***246**, 167(1995).
- ²¹ P.Melinon,

- P.Keghelian, A.Perez, B.Champagnon, Y.Guyot, L.Saviot, E.Reny, C.Cros, M.Pouchard, A.J.Jianoux, Phys.Rev.B**59**, 10099(1999).
- ²² O.Zhou, S.Kuroshima, K.tanigaki, unpublished.
- ²³ S.Bolev and S.C.Sevov, J.Am.Chem.Soc.**121**, 3795(1999).
- ²⁴ M.T.Yin and M.L.Cohen, Phys.Rev.B**26**, 5668(1982).
- ²⁵ M.C.Payne, M.T.Teter, D.C.Allen, T.A.Arias, J.D.Joannopoulos, Rev.Mod.Phys.**64**, 1045(1992).
- ²⁶ A.Buldum, S.Ciraci, C.Y.Fong, J.S.Nelson, Phys.Rev.B**59**, 5120(1999).
- ²⁷ D. R. Hamann, M. Schluter, and C. Chiang, Phys.Rev.Lett.**43**, 1494(1979); G.B.Bachelet, D.R.Hamann, and M.Schluter, Phys.Rev.B**26**, 4199(1982); D.R.Hamann, Phys.Rev.B**40**, 2980(1989).
- ²⁸ L.Kleinman, D.M.Bylander, Phys.Rev.Lett.**48**, 1425(1982).
- ²⁹ D.M.Ceperley and B.J.Alder, Phys.Rev.Lett.**45**, 566(1980); J. Perdew and A.Zunger, Phys.Rev.B**23**, 5048(1981).
- ³⁰ H.J.Monkhorst, J.D.Pack, Phys.Rev.B**13**, 5188(1976).
- ³¹ CASTEP is an *ab initio* program with plane-wave pseudopotential package distributed by MSI.
- ³² D.A.Papaconstantopoulos, *Handbook of the Band Structure of Elemental Solids*, (Plenum Press, New York, 1986).
- ³³ C.Kittel, *Introduction to Solid State Physics*, (John Wiley & Sons, New York, 1986).